

FUJIPOLY Data Sheet

SARCON PG150A series


Extremely Compressible Gap Filler Type

FEATURES


Highly Conformable and Non-Flammable, Higher Thermal interface materials.

SARCON Extremely Compressible Gap Filler Type (Putty Type) is a highly conformable, thermally conductive, non-flammable interface materials. The surface consistency is excellent for filling small air gaps and uneven mating surface, making reliable contact with various shapes and sizes of components.

CONSTRUCTION

Series	Characteristics	Constructions
SARCON PG150A	Silicone compound with double sticky surfaces and Thermal Conductivity of PG150A material is 15.0W/m-K by using Hot Disk.	 Plain Type

RECOMMENDED APPLICATION

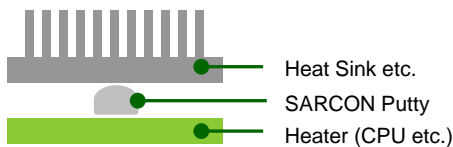

To determine the size and volume of SARCON Putty Type to be used, follow this helpful example:



EX.
Original Gap : $V=90.0\text{mm}^3$
(0.4mm H x 15mm W x 15mm L)

Decide Thickness of SARCON depend on the compression force
e.g. Decided Thickness = 1.0mm

$$\sqrt{90.0(V) / 1 (T)} = 9.486 \text{ mm}$$

⇒ use ; 9.5 mm x 9.5 mm x 1.0 mmT

THERMAL RESISTANCE

Unit : K-cm²/W (K-in²/W)

Compression Force	0.3mmT	0.5mmT	1.0mmT	1.5mmT	2.0mmT
100kPa /14.5psi	0.18 (0.03)	0.28 (0.04)	0.51 (0.08)	0.80 (0.12)	1.03 (0.16)
300kPa /43.5psi	0.16 (0.02)	0.25 (0.04)	0.45 (0.07)	0.55 (0.09)	0.59 (0.09)
500kPa /72.5psi	0.14 (0.02)	0.20 (0.03)	0.27 (0.04)	0.29 (0.04)	0.30 (0.05)

Test method : Fujipoly Test method, FTM-P3050 by TIM Tester 1400 which is ASTM D5470 equivalent

• Specimen Area : DIA.33.0mm (1.30in)

TYPICAL PROPERTIES

Properties		unit		PG150A	Test method	Specimen
Physical Properties	Color	-		Gray	Visual	-
	Specific Gravity	-		3.0	ASTM D792	A
Electrical Properties	Volume Resistivity	Ohm-m		3.0x10 ⁹	ASTM D257	B
	Breakdown Voltage	kV/mm (volts/mil)		10 (254)	ASTM D149	C
	Dielectric Strength	kV/mm (volts/mil)		7 (178)	ASTM D149	C
	Dielectric Constant	-	50Hz	8.8	ASTM D150	A
			1kHz	8.2		
			1MHz	7.5		
	Dissipation Factor	-	50Hz	0.200	ASTM D150	A
			1kHz	0.041		
1MHz			0.024			
Thermal Properties	Thermal Conductivity	W/m-K		15.0	ISO 22007-2	-
	Useful Temperature	°C (°F)		-40 to +150 (-40 to +302)	-	-
	Low molecular Siloxane	wt%		D ₃ to D ₁₀ 0.0010	Gas Chromatography	-
	Flame Retardant	-		V-0 equivalent	UL 94	-

- Each Specimens are cured for measurement.
- Specimen A : 2mmT
- Specimen B : 100mmW × 100mmL × 1mmT
- Specimen C : 120mmW × 120mmL × 1mmT

COMPRESSION FORCE

Unit : N/6.4cm² (psi)

Compression Ratio	0.3mmT	0.5mmT	1.0mmT	1.5mmT	2.0mmT
10%	72 (16.3)	104 (23.6)	143 (32.4)	88 (19.9)	65 (14.7)
20%	160 (36.3)	261 (59.1)	332 (75.2)	213 (48.3)	179 (40.6)
30%	322 (73.0)	504 (114.2)	552 (125.1)	421 (95.4)	362 (82.0)
40%	552 (125.1)	703 (159.3)	766 (173.5)	592 (134.1)	444 (100.6)
50%	775 (175.6)	901 (204.1)	1110 (251.5)	864 (195.8)	579 (131.2)
Sustain 50%	557 (126.2)	461 (104.4)	353 (80.0)	228 (51.7)	152 (34.4)

Test method : Measured by ASTM D575-91 for reference

- Specimen Area : DIA.28.6mm (1.13in)
- Platen Area : DIA. 28.6mm (1.13in)
- Sustain 50% : Sustain 50% at 1 minute later
- Compression Velocity : 5.0mm/minute

DURABILITYUnit : K-cm²/W

Test Property	Compression Ratio	70°C					150°C				
		Initial	100hrs	250hrs	500hrs	1,000hrs	Initial	100hrs	250hrs	500hrs	1,000hrs
Thermal Resistance	30%	0.47	0.46	0.40	0.44	0.46	0.51	0.48	0.44	0.52	0.48
	70%	0.30	0.32	0.32	0.31	0.31	0.32	0.30	0.32	0.32	0.37

Test Property	Compression Ratio	60°C/95%RH					85°C/85%RH				
		Initial	100hrs	250hrs	500hrs	1,000hrs	Initial	100hrs	250hrs	500hrs	1,000hrs
Thermal Resistance	30%	0.48	0.44	0.44	0.44	0.40	0.48	0.47	0.46	0.47	0.45
	70%	0.30	0.31	0.31	0.33	0.31	0.37	0.35	0.35	0.35	0.33

Test Property	Compression Ratio	-40°C(30min)⇄+125°C(30min)				
		Initial	100hrs	250hrs	500hrs	1,000hrs
Thermal Resistance	30%	0.48	0.50	0.50	0.50	0.48
	70%	0.27	0.24	0.23	0.28	0.29

- Thermal Resistance : Measured by using ASTM D5470 modified, refer to Fujipoly Test method FTM P-3030.

reduced temperature

- Specimen Area : 30% = 15mm square , initial thickness = 1.0mm

-40°C = -40°F

- Specimen Area : 70% = 10mm square , initial thickness = 1.0mm

60°C = 140°F

(Specimen is sandwiched between aluminum blocks.)

70°C = 158°F

125°C = 257°F

150°C = 302°F

TYPES AND CONFIGURATION

Series	Product Name	Thickness	Sheet Size
SARCON PG150A	PG150A-00-30GY	0.3mm ±0.06mm	300mm × 200mm (Recommended Usable Size:290mm×190mm)
	PG150A-00-50GY	0.5mm ±0.10mm	
	PG150A-00-100GY	1.0mm ±0.15mm	
	PG150A-00-150GY	1.5mm ±0.20mm	
	PG150A-00-200GY	2.0mm ±0.30mm	

HANDLING NOTES

- It is recommended to compress the material with the equal ratio on the whole surface. Partial excessive stress may also result in excessive silicone oil exudation.

WARRANTY STATEMENT

- Fujipoly has been utilizing Hot Disk method and TIM Tester method since Fujipoly defined them as Fujipoly standard.
- Properties of the products may be revised due to some changes for improving performance.
- Properties values in this document are not specification or guaranteed.
- This product is made of silicone, and silicone oil may exude from the product.
- This product is made of silicone, and low molecular siloxane may vaporize depending on operating conditions.
- The product is designed, developed, and manufactured for general industrial use only. Never use for medical, surgical, and/or relating purposes. Never use for the purpose of implantation and/or other purposes by which a part of or whole product remains in human body.
- Before using, a safety must be evaluated and verified by the purchaser.
- Contents described in the document do not guarantee the performances and qualities required for the purchaser's specific purposes. The purchaser is responsible for pre-testing the product under the purchaser's specific conditions and for verifying the expected performances.
- Statements concerning possible or suggested uses made herein may not be relied upon, or be constructed, as a guaranty of no patent infringement.
- Copyright© 2024 FUJIPOLY